



Research and Sponsored Programs  
Office of the Director

120 Ozark Hall  
Fayetteville, Arkansas 72701  
(501) 575-3845  
(501) 575-3846 (FAX)

May 24, 1996

Defense Technical Information Center  
8725 John J. Kingman Road, Suite 0944  
Fort Belvoir, VA 22060-6218


*RE: Grant #N00014-92-J-2016*  
*PI: Dr. Min Xiao*

To Whom It May Concern:

Enclosed please find a completed copy of Standard Form (SF) 298 "Report Document Page" for the referenced grant including your copy of the final technical report. We are very sorry for any inconvenience this may have caused.

Thank you for your assistance.

Sincerely,

  
Jane L. Treat  
Associate Director



JLT/kms  
Enclosure  
cc: ONRRR, Atlanta, GA (1 copy)  
Director, NRL (1 copy)  
M. Xiao

19960604 082

DTIC QUALITY INSPECTED 1

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0138

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0138), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE 5/24/96	3. REPORT TYPE AND DATES COVERED FINAL REPORT/8/1/92 - 7/31/95	
4. TITLE AND SUBTITLE AASERT: Optical Characterization of Diamond Films for Superconducting			5. FUNDING NUMBERS N00014-92-J-2016	
6. AUTHOR(S) Min Xiao				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Board of Trustees University of Arkansas 120 Ozark Hall Fayetteville, AR 72701			8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Department of the Navy Naval Research Laboratory 4555 Overlook Avenue, SW Washington, DC 20375-5320			10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES				
12a. DISTRIBUTION/AVAILABILITY STATEMENT UNLIMITED			12b. DISTRIBUTION CODE UNL	
13. ABSTRACT (Maximum 200 words)  We have discovered and have characterized a new nonlinear optical effect. The effect is studied in a strontium barium niobate substrate material but should be observable in diamond photorefractive substrates as well. We show that a quasi-stead-state photorefractive spatial soliton forms a waveguide structure in the bulk of a photorefractive material. Although the optically induced waveguide is formed by a very low-power (microwatts) soliton beam, it can guide a powerful (watt) beam of a longer wavelength at which the medium is nonphotosensitive. Furthermore, the waveguide survives, either in the dark or when guiding the longer-wavelength beam, for a long time after the soliton beam is turned off. We take advantage of the solitons' property of evolution from a relatively broad input beam into a narrow channel and show that the soliton induces a tapered waveguide (an optical funnel) that improves the coupling efficiency of light into the waveguiding structure.				
14. SUBJECT TERMS Optical characterization, soliton			15. NUMBER OF PAGES 9	
			16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT Unlimited	



Research and Sponsored Programs  
Office of the Director

120 Ozark Hall  
Fayetteville, Arkansas 72701  
(501) 575-3845  
(501) 575-3846 (FAX)

February 12, 1996

Dr. Jim Butler  
Code 6170  
Naval Research Laboratory  
4555 Overlook Avenue, SW  
Washington, DC 20375-5320

RE: N00014-92-J-2016  
PI: Dr. Min Xiao

Dear Dr. Butler:

Enclosed please find an original and two (2) copies of a Final Technical Report for the above referenced grant.

The University of Arkansas sincerely appreciates the Naval Research Laboratory's support of this project.

Sincerely,

Jane L. Treat  
Associate Director

JLT/kms  
Enclosure

cc: ONRRR, Atlanta, GA (1 copy)  
Director, NRL (1 copy)  
DTIC, Alexandria, VA (1 copy) ✓  
M. Xiao

DTIC QUALITY INSPECTED 3

**AASERT: OPTICAL CHARACTERIZATION OF DIAMOND  
FILMS FOR SUPERCONDUCTING**

**AWARD NO:** N00014-92-J-2016

**PRINCIPAL INVESTIGATOR:** Professor Min Xiao

**STUDENT:** Matthew Morin

**ABSTRACT**

We have discovered and have characterized a new nonlinear optical effect. The effect is studied in a strontium barium niobate substrate material but should be observable in diamond photorefractive substrates as well. We show that a quasi-stead-state photorefractive spatial soliton forms a waveguide structure in the bulk of a photorefractive material. Although the optically induced waveguide is formed by a very low-power (microwatts) soliton beam, it can guide a powerful (watt) beam of a longer wavelength at which the medium is nonphotosensitive. Furthermore, the waveguide survives, either in the dark or when guiding the longer-wavelength beam, for a long time after the soliton beam is turned off. We take advantage of the solitons' property of evolution from a relatively broad input beam into a narrow channel and show that the soliton induces a tapered waveguide (an optical funnel) that improves the coupling efficiency of light into the waveguiding structure.

**OBJECTIVE**

While the original objective was to optically characterize diamond substrates we discovered during our investigations a new optical effect which could lead to a new technique for optical wiring in a diamond substrate used in building MCM's. As a result, our objective became to characterize our discovery.

19960223 091

## INTRODUCTION AND PREVIOUS WORK

It has been established for several years that spatial Kerr-type solitons induce guidance of a typically much weaker beam<sup>1,2</sup> through cross-phase modulation. In fact, the optical control of one beam by another has interesting potential applications in all-optical switching and beam-steering waveguide devices.<sup>3,4</sup> All these effects are based on Kerr-type solitons, and, as such, they carry over their characteristic properties: (i) waveguides induced by bright Kerr solitons exist only in one transverse dimension<sup>1</sup> (implying that all potential device applications must be planar), (ii) the dimensions of the induced waveguide depend on the soliton intensity, and (iii) the guided beam is much weaker than the soliton (guiding) beam.<sup>1</sup>

Photorefractive solitons<sup>5</sup> have been shown to exist in several forms. Quasi-steady-state solitons<sup>13</sup> appear during the slow screening process of a field applied externally to a photorefractive crystal. Solitons of this type are transient by nature, and we refer to their time window of existence as a quasi-steady state. Their most distinct properties are independence of the absolute light intensity.<sup>5-8, 12, 13</sup> Experimental observations have proved the existence of one- and two- dimensional bright solitons,<sup>7-9</sup> planar dark solitons, and vortex solitons.<sup>12, 13</sup> The second type of photorefractive soliton is the screening soliton,<sup>14</sup> which appears in the steady state, after the external field is screened nonuniformly as a result of the transversely nonuniform intensity distribution. This effect is local and results in an index perturbation that is inversely proportional to the sum of the optical and dark irradiances. Recent experimental observations have confirmed the existence of one- and two-dimensional screening solitons.<sup>15, 16</sup> The third type of photorefractive soliton exists in materials that are both photorefractive and photovoltaic. These photovoltaic solitons<sup>17</sup> stem from photovoltaic currents that generate an index perturbation analogous to the nonlinearity in a saturable absorber. A recent observation<sup>18</sup> confirmed the existence of dark photovoltaic solitons in  $\text{LiNbO}_3$ . Some of these experimental observations<sup>18, 19</sup> have shown that illumination of the crystal by a second

(uniform) beam in the presence of the soliton leads to guidance of light in the soliton region. Finally, a recent paper predicted the existence of photorefractive vector solitons.<sup>20</sup>

## RESULTS IN AASERT PROGRAM

In the AASERT program we show that photorefractive spatial solitons may serve as optical waveguides for other optical beams. Photorefractive solitons are especially attractive for light-induced waveguiding because they form in two transverse dimensions and require very little power (they exist even at microwatts or less). Furthermore, since the nonlinearity is based on space-charge fields that result from charges occupying deep traps, all photorefractive solitons leave behind them a waveguide structure that persists in the dark. One can utilize this memory property further by using the induced waveguides to guide light of nonphotosensitive wavelengths (typically much longer than that of the soliton) that cannot photoexcite the trapped charges. In this scheme a very weak photorefractive soliton beam can guide and control a very intense beam. Another interesting manifestation of the soliton guidance is the evolution from a relatively broad input beam into a narrow channel, where the photorefractive soliton induces a tapered waveguide, or an optical funnel. We study the guidance properties and measure the lifetime of these soliton-induced waveguides. We then use these waveguides to guide a near-infrared beam of intensity  $2 \times 10^4 \text{ W/cm}^2$ , approximately 5 orders of magnitude larger than that of the soliton beam (roughly  $0.1 \text{ W/cm}^2$ ). Finally, we point out that the two-dimensional soliton trapping properties<sup>7 - 9, 12, 13, 15</sup> hold the promise of forming light needles (two-dimensional waveguides) in a bulk material. These and related two-dimensional guidance experiments by bright and vortex photorefractive solitons are currently under investigation.

Creating optical waveguides with quasi-steady-state photorefractive solitons seems to be preferable to inducing them with the screening (steady-state) solitons for several reasons. First, we have found experimentally that the quasi-stead-state solitons require a

lower trapping voltage than the screening solitons in the same material (in  $\text{Sr}_{0.6}\text{Ba}_{0.4}\text{Nb}_2\text{O}_6$ , for example, quasi-steady-state solitons require  $\sim 400$  V/cm, whereas screening solitons require  $\sim 3 - 4$  kV/cm. Second, the quasi-steady-state solitons appear much earlier in time than the screening solitons of the same intensities ( $\sim 100$  ms versus  $\sim 1$  s for  $\sim 1\text{ }\mu\text{W}$  power on a  $20\text{-}\mu\text{m}$  bright soliton in SBN). third, for quasi-steady-state solitons the trapping is independent of the beam intensity (for an intensity much larger than the dark irradiance), while bright screening solitons are narrowest for soliton peak intensities of the order of the dark irradiance.<sup>14, 15</sup> This implies that bright screening solitons require uniform background illumination<sup>15, 16</sup> to generate artificial dark irradiance; otherwise either their trapping voltages become very large (for peak intensities much larger than the dark irradiance) or their response time (dielectric relaxation time) becomes extremely long (for peak intensities of the order of the dark irradiance). The immediate consequence is that they require much higher total laser powers than the quasi-steady-state solitons do. All these reasons motivate the study of optical guiding with quasi-steady-state solitons.

In our work we restrict our experiments to guidance with quasi-steady-state dark photorefractive solitons. It is, however, obvious that the other realizations of these solitons, namely, the one- and two-dimensional bright solitons and the dark vortex solitons, should be explored as well. We used an experimental setup similar to that shown in Fig. 1 of Ref. 13. For the best guidance results, one needs to capture the index profile that traps the dark solitons by shutting off the illumination at the soliton wavelength at the point in time when they are the narrowest (before screening effects start to take place). Typical times for generating dark solitons at 457-nm wavelength and of  $\sim 20\text{-}\mu\text{m}$  size at  $\sim 75\text{-}\mu\text{W}$  power are of the order of 700 ms. We generate the soliton waveguides in rhodium-doped SBN:60 by applying negative voltages of  $\sim 400$  V (parallel to the  $c$  axis) across the 5-mm-wide crystal. To generate the planar dark solitons we launch a dark notch

on an extraordinarily polarized beam that possesses a  $\pi$  phase jump in its center. The notch is obtained by insertion of a thin glass slide in one half of the beam, and the phase is adjusted (until the notch is obtained) by tilting the glass slide. The beam is then focused and enters the crystal with a notch size of 30  $\mu\text{m}$  (FWHM). The output beam is split and monitored by a photodetector (to locate the quasi-steady-state time window) and by a CCD camera (to watch the image of the beam at the crystal output face). A second CCD camera is located above the crystal so that we can image and observe the propagation of the beam throughout the entire crystal length at any given time (in this manner the photographs in Refs. 8 and 12 were taken). A computer-controlled shutter located close to the argon laser output blocks the 457-nm light at the point when the dark soliton is narrowest. The top-view color photograph of the dark soliton is shown in Plate I(a). A careful examination of this plate reveals that in the dark notch narrows at the first 2 mm of the crystal and forms a dark funnel before reaching its stationary (nonvarying) soliton size. For comparison, we show in Plate I(b) a color photograph of the dark notch experiencing normal diffraction when no voltage is applied to the crystal.

After the 457-nm beam that generated the dark soliton is blocked, we launch an extraordinarily polarized 633-nm He - Ne laser beam into the induced waveguide. Plate II(a) shows a top-view color photograph of the red beam guided to  $\sim 11\text{-}\mu\text{m}$  diameter (FWHM) by the dark (blue) soliton-induced waveguide. The guided beam is funneled from a broader input into a slightly narrower width. In this manner the dark soliton induces an optical funnel that resembles tapered waveguide. For comparison, we show in Plate II(b) a top-view color photograph of the red beam in the normal diffraction regime (zero voltage or ordinary polarization), where the beam diameter (FWHM) at the crystal exit face is 55  $\mu\text{m}$ . Figure 1 shows the profiles of the He - Ne beam at the entrance face of



the crystal (left), at the exit face in the normal diffraction regime (no voltage, middle), and when guided by the dark soliton (right).

We have measured the lifetime of the induced waveguide guiding a red He - Ne beam and a 1319-nm Nd:YAG beam as a function of the guided (or probe) beam intensity when the soliton beam is blocked. Since the soliton is formed by a space-charge field that results from charges trapped in deep traps, we expect that at nonphotosensitive wavelengths (typically much longer than that of the soliton) the photoexcitation from the deep traps will diminish and the waveguide will persist for very long times. Some slight degradation is expected since the guided beam will excite charges from shallower traps that will mask (in part) the field generated by the charges trapped in the deep traps. Figure 2 shows the lifetime of the soliton waveguide measured from the moment the soliton beam is blocked as a function of the guided beam intensity for the 1319-nm Nd:YAG beam. The curve follows an accurate inverse-intensity dependence. A similar but much shorter time curve was observed with the guided He - Ne beam. In all cases the power of the guided beam greatly exceeds the power of the soliton beam. We expect that a very intense ( $1\text{-MW/cm}^2$ ) guided beam near 1500 nm will not perturb the soliton-induced waveguide if short pulses are used so that no thermal effects are present.

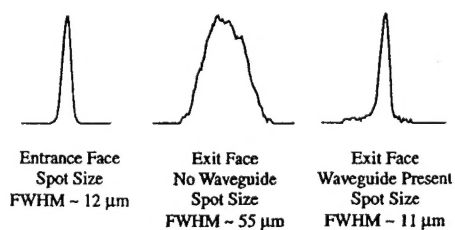


Fig. 1. Profiles of the red He-Ne beam at the entrance face of the crystal (left), at the exit face of the crystal in the normal diffraction regime (no voltage, middle), and when guided by the dark soliton (right).

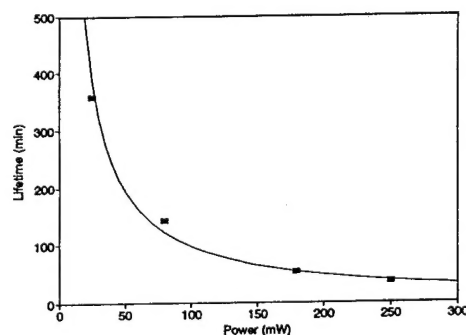


Fig. 2. Lifetime of the soliton-induced waveguide, measured from the moment the soliton is blocked, as a function of the guided beam intensity for a 1319-nm Nd:YAG beam. The lifetime follows an accurate inverse-intensity dependence.

## CONCLUSIONS

In conclusion, we have demonstrated the use of quasi-steady-state photorefractive dark spatial solitons as waveguides for intense beams of a longer wavelength. Although the soliton is formed by a beam as weak as a few microwatts, it guides near-infrared beams of the order of 1-W power. The waveguides form in a bulk material and persist for a long time after the soliton beam is blocked, even in the presence of an intense near-infrared beam. In current experiments we are testing the possibility of generating two-dimensional waveguides that are based on the ability of photorefractive solitons to trap in both transverse dimensions.

While these conclusions apply to nonlinear photorefractive materials in general, they should be observable in doped diamond substrates due to their nonlinear properties. Such an observation would be exciting since it might lead to reconfigurable optical interconnects in diamond substrates for MCM's.

## REFERENCES

1. R. De La Fuente, A. Barthelemy, and C. Froehly, *Opt. Lett.* **16**, 793 (1991).
2. B. Duthier-Davies and X. Yang, *Opt. Lett.* **17**, 1755 (1992).
3. C. Bosshard, P. V. Mamyshev, and G. I. Stegeman, *Opt. Lett.* **19**, 90 (1994).
4. P. V. Mamyshev, A. Villeneuve, G. I. Stegeman, and J. S. Aitchinson, *Electron Lett.* **30**, 726 (1994).
5. M. Segev, B. Crosignani, A. Yariv, and B. Fischer, *Phys. Rev. Lett.* **68**, 923 (1992).
6. B. Crosignani, M. Segev, D. Engin, P. DiPorto, A. Yariv, and G. Salamo, *J. Opt. Soc. Am. B* **10**, 446 (1993).
7. G. Duree, J. L. Shultz, G. Salamo, M. Segev, A. Yariv, B. Crosignani, P. DiPorto, E. Sharp, and R. R. Neurgaonkar, *Phys. Rev. Lett.* **71**, 533 (1993).


8. M. Segev, A. Yariv, G. Salamo, G. Duree, J. L. Shultz, , B. Crosignani, P. DiPorto, and E. Sharp, *Opt. Photon. News* **4**(12), 8 (1993).
9. G. Duree, G. Salamo, M. Segev, A. Yariv, B. Crosignani, P. DiPorto, and E. Sharp, *Opt. Lett.* **19**, 1195 (1994).
10. M. Segev, A. Yariv, B. Crosignani, P. DiPorto, G. Duree, G. Salamo, and E. Sharp, *Opt. Lett.* **19**, 1296 (1994).
11. D. N. Christodoulides and M. I. Carvalho, *Opt. Lett.* **19**, 1714 (1994).
12. M. Segev, G. Salamo, G. Duree, M. Morin, B. Crosignani, P. DiPorto, and A. Yariv, *Opt. Photon. News* **5**(12), 9 (1994).
13. G. Duree, M. Morin, G. Salamo, M. Segev, B. Crosignani, P. DiPorto, E. Sharp, and A. Yariv, *Phys. Rev. Lett.* **74**, 1978 (1995).
14. M. Segev, G. C. Valley, B. Crosignani, P. DiPorto, and A. Yariv, *Phys. Rev. Lett.* **73**, 3211 (1994).
15. M. Shih, M. Segev, G. C. Valley, G. Salamo, B. Crosignani, and P. DiPorto, *Electron. Lett.* **31**, 826 (1995).
16. Observations of steady-state self-focusing effects in  $\text{Bi}_{12}\text{TiO}_{20}$  were presented by M. D. Iturbe-Castillo, P. A. Marquez-Aguilar, J. J. Sanchez-Mondragon, S. Stepanov, and V. Vysloukh, *Appl. Phys. Lett.* **64**, 408 (1994).
17. G. C. Valley, M. Segev, B. Crosignani, A. Yariv, M. M. Fejer, and M. Bashaw, *Phys. Rev. A* **50**, 4457 (1994).
18. M. Taya, M. Bashaw, M. M. Fejer, M. Segev, and G. C. Valley, *Phys. Rev. A* **52**, 3095 (1995). This observation was also reported by G. C. Valley, M. Segev, A. Yariv, M. Taya, M. Fejer, M. Bashaw, B. Crosignani, and P. DiPorto, "Spatial photovoltaic and screening solitons in photorefractive materials," in *Proceedings of IEEE Conference on Nonlinear Optics* (Institute of Electrical and Electronics Engineers, New York, 1994).

19. M. D. Iturbe-Castillo, P. A. Marquez-Aguilar, J. J. Sanchez-Mondragon, S. Stepanov, M. B. Klein, and B. A. Wechsler, presented at Optical Society of America Annual Meeting, Dallas, Tex., October 4-10, 1994, paper WD4.
20. M. Segev, G. C. Valley, S. R. Singh, M. I. Carvalho, and D. N. Christodoulides, Opt. Lett. **20**, 1764 (1995).

#### MAJOR STUDENT PUBLICATIONS

- "Waveguides formed by quasi-steady-state photorefractive spatial solitons", M. Morin, G. Duree, M. Segev, and G. Salamo, Opt. Lett. **20**, 2066, (1995).
- "Dark Photorefractive Solitons, G. Duree, M. Morin, M. Segev, and G. Salamo, Phys. Rev. Lett. **74**, 1978 (1995).

(a)

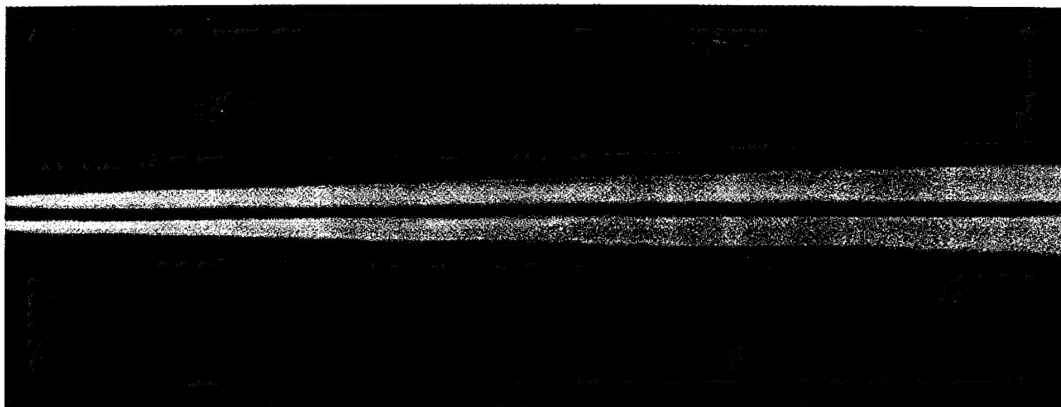

(b)


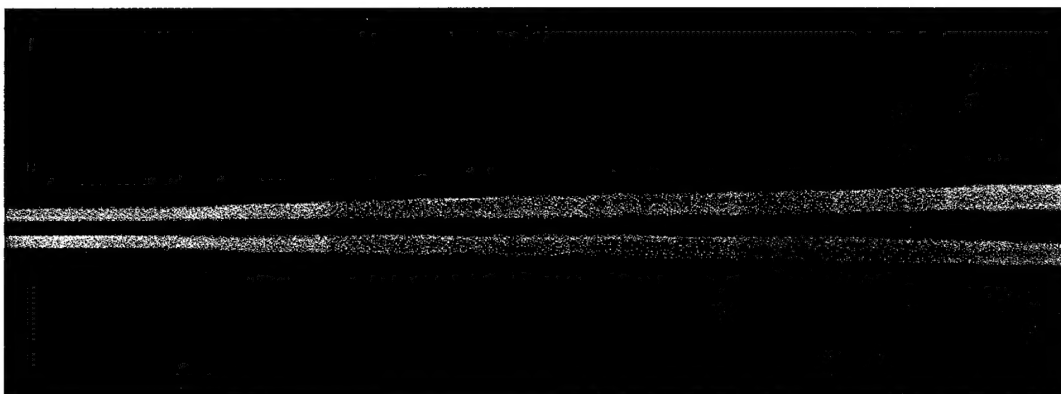


Plate I. Top-view color photographs of (a) the dark soliton and (b) the normally diffracting dark notch when the voltage applied to the crystal is set to zero.

(a)

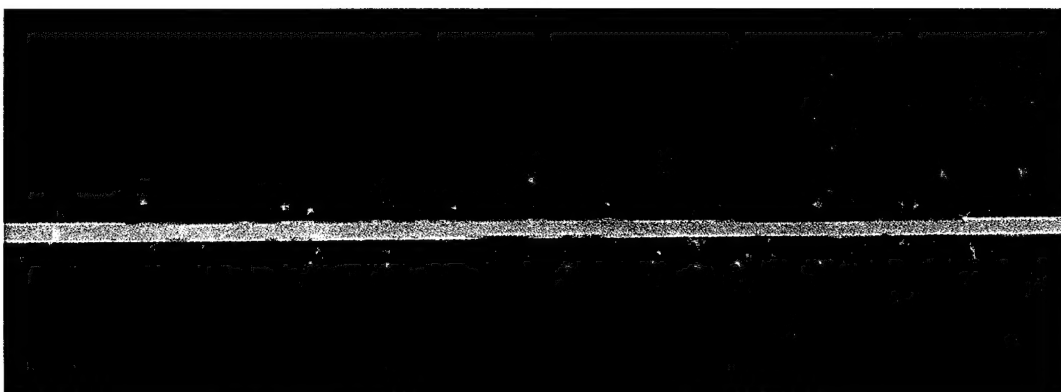

(b)

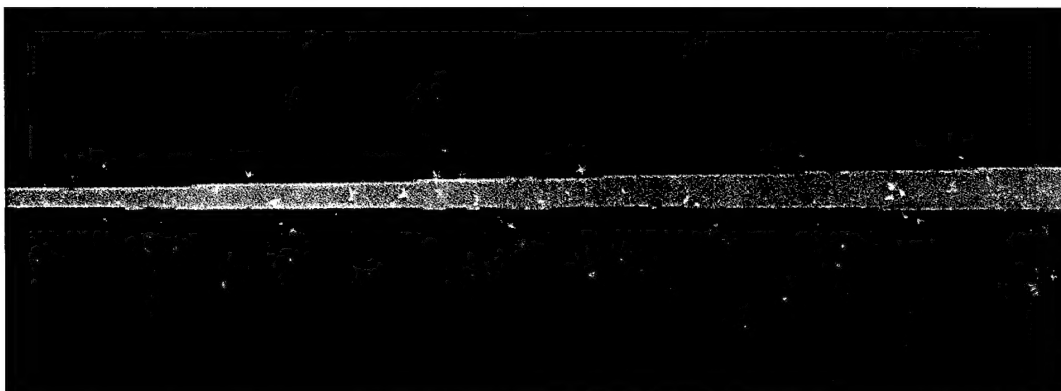


Plate II. Top-view color photographs of (a) the guided red He-Ne beam and (b) the red beam in the normal diffraction regime.